

VECTRA® MT®1310

Liquid Crystal Polymer

Vectra® MT1310 VF3001 (natural) is a 30% glass reinforced, easy flow LCP grade for injection molding.

Vectra® MT1310 VF3001 (natural) is a special grade developed for medical industry applications and complies with:

- Food Contact Substance Notification (FCN) No. 742 of the Food and Drug Administration (FDA) and is listed in the Drug Master File (DMF 8464) and the Device Master File (MAF 315)
- the corresponding EU and national registry regulatory requirements
- biocompatibility in tests corresponding to USP 23 Class VI/ISO 10993
- low residual monomers
- no animal products

The Standard for the Industry. Excellent balance of properties, including easy flow, easy processing, thermal stability, chemical resistance, mechanical and electrical properties. Suitable for vapor phase surface mount electrical and electronic devices.

Chemical abbreviation according to ISO 1043-1 : LCP

Inherently flame retardant

Product information

Resin Identification	LCP-GF30	ISO 1043
Part Marking Code	>LCP-GF30<	ISO 11469

Rheological properties

Moulding shrinkage, parallel	0.2 %	ISO 294-4, 2577
Moulding shrinkage, normal	0.4 %	ISO 294-4, 2577

Typical mechanical properties

Tensile modulus	15000 MPa	ISO 527-1/-2
Tensile stress at break, 5mm/min	190 MPa	ISO 527-1/-2
Tensile strain at break, 5mm/min	2.1 %	ISO 527-1/-2
Flexural modulus	15000 MPa	ISO 178
Flexural strength	260 MPa	ISO 178
Compressive modulus	14500 MPa	ISO 604
Compressive stress at 1% strain	138 MPa	ISO 604
Tensile creep modulus, 1h	12600 MPa	ISO 899-1
Tensile creep modulus, 1000h	10900 MPa	ISO 899-1
Charpy notched impact strength, 23°C	46 kJ/m ²	ISO 179/1eA
Izod notched impact strength, 23°C	33 kJ/m ²	ISO 180/1A
Hardness, Rockwell, M-scale	85	ISO 2039-2
Poisson's ratio	0.33 ^[C]	

[C]: Calculated

Thermal properties

Melting temperature, 10°C/min	280 °C	ISO 11357-1/-3
Temperature of deflection under load, 1.8 MPa	235 °C	ISO 75-1/-2
Temperature of deflection under load, 0.45 MPa	250 °C	ISO 75-1/-2
Temperature of deflection under load, 8 MPa	190 °C	ISO 75-1/-2
Vicat softening temperature, 50°C/h 50N	160 °C	ISO 306

VECTRA® MT® 1310

Liquid Crystal Polymer

Coefficient of linear thermal expansion (CLTE), parallel	6 E-6/K	ISO 11359-1/-2
Coefficient of linear thermal expansion (CLTE), normal	23 E-6/K	ISO 11359-1/-2

Flammability

Burning Behav. at thickness h	V-0 class	IEC 60695-11-10
Oxygen index	45 %	ISO 4589-1/-2

Electrical properties

Relative permittivity, 100Hz	4.2	IEC 62631-2-1
Relative permittivity, 1MHz	3.7	IEC 62631-2-1
Dissipation factor, 100Hz	160 E-4	IEC 62631-2-1
Dissipation factor, 1MHz	180 E-4	IEC 62631-2-1
Volume resistivity	1E13 Ohm.m	IEC 62631-3-1
Surface resistivity	>1E15 Ohm	IEC 62631-3-2
Electric strength	31 kV/mm	IEC 60243-1
Comparative tracking index	175	IEC 60112
Arc Resistance	140 s	UL 746B

Physical/Other properties

Humidity absorption, 2mm	0.04 %	Sim. to ISO 62
Density	1610 kg/m ³	ISO 1183

Injection

Drying Recommended	yes
Drying Temperature	150 °C
Drying Time, Dehumidified Dryer	4 - 6 h
Processing Moisture Content	≤0.01 %
Melt Temperature Optimum	290 °C
Min. melt temperature	285 °C
Max. melt temperature	295 °C
Screw tangential speed	0.2 - 0.3 m/s
Mold Temperature Optimum	100 °C
Min. mould temperature	80 °C
Max. mould temperature	120 °C
Back pressure	3 MPa
Ejection temperature	225 °C

Characteristics

Processing	Injection Moulding
Delivery form	Pellets
Special characteristics	Flame retardant, Light stabilised or stable to light, U.V. stabilised or stable to weather, Heat stabilised or stable to heat

VECTRA® MT®1310

Liquid Crystal Polymer

Additional information

Injection molding

Preprocessing

Vectra resins are well known for their excellent thermal and hydrolytic stability. In order to ensure these properties are optimum, the resin should be dried correctly prior to processing. The Vectra MT-grades MT1300, MT1305, MT1310, MT1335, MT1340 and MT1345 should be dried at 150 °C for a minimum of 4 hours in a desiccant dryer.

Processing

A three-zone screw evenly divided into feed, compression, and metering zones is preferred. A higher percentage of feed flights may be needed for smaller machines: 1/2 feed, 1/4 compression, 1/4 metering.

Vectra LCPs are shear thinning, their melt viscosity decreases quickly as shear rate increases. For parts that are difficult to fill, the molder can increase the injection velocity to improve melt flow.

Processing Notes

Pre-Drying

VECTRA should in principle be predried. Because of the necessary low maximum residual moisture content the use of dry air dryers is recommended. The dew point should be $\leq -40^{\circ}\text{C}$. The time between drying and processing should be as short as possible.


Storage

For subsequent storage of the material in the dryer until processed the temperature does not need to be lowered for grades A, B, C, D and V ($\leq 24\text{ h}$).

VECTRA® MT® 1310

Liquid Crystal Polymer

Stress-strain

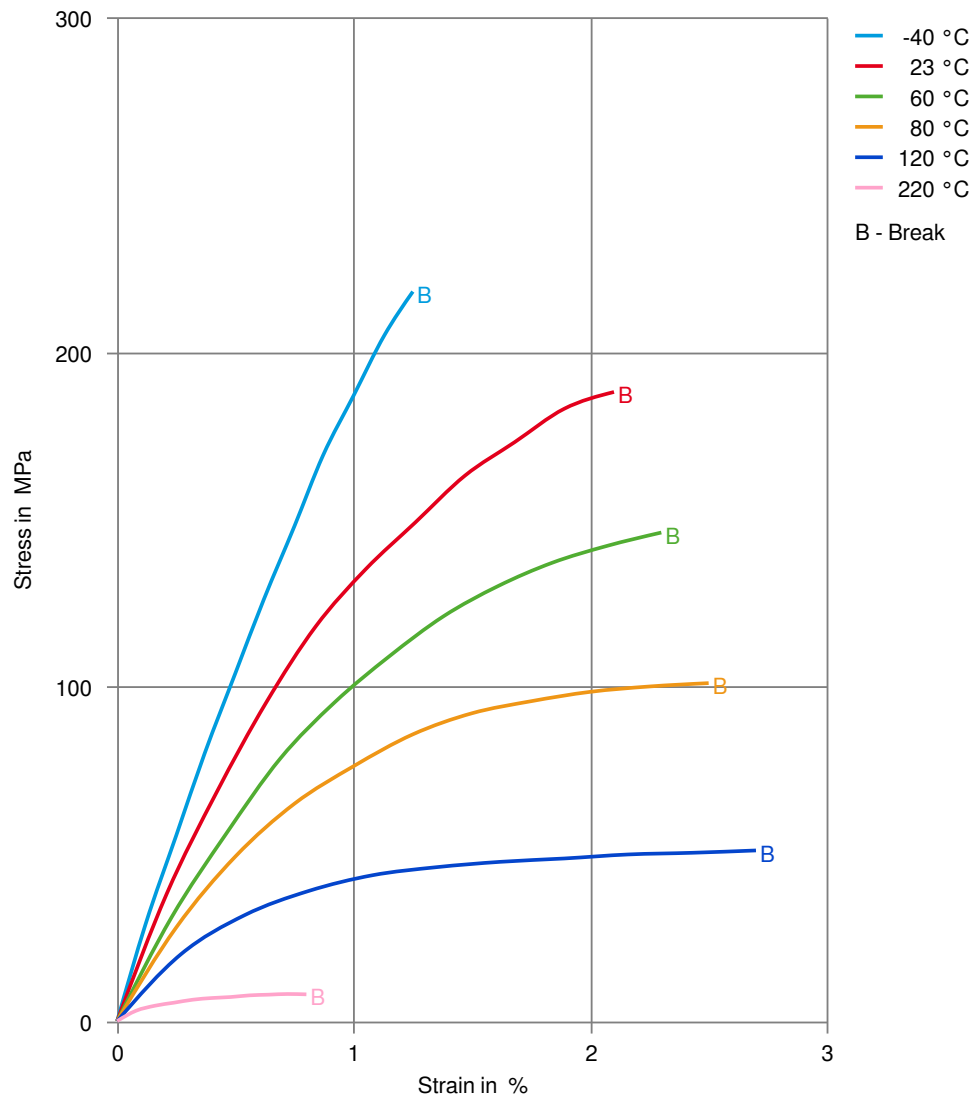

VECTRA® MT® 1310

Liquid Crystal Polymer

Secant modulus-strain

