

IMPET® 2700 GV1/30 - PET

Description


30% glass fiber reinforced

30% glass filled Polyethylene terephthalate (PET) with high flowability, excellent gloss, high modulus, and high heat deflection temperature.


Physical properties	Value	Unit	Test Standard
Density	99.9	lb/ft ³	ISO 1183
Molding shrinkage, parallel (flow)	0.2 - 0.4	%	ISO 294-4, 2577
Molding shrinkage, transverse normal	0.7 - 0.9	%	ISO 294-4, 2577
Water absorption, 23°C-sat	0.4	%	Sim. to ISO 62
Humidity absorption, 23°C/50%RH	0.15	%	ISO 62
Viscosity number	1940	in ³ /lb	ISO 307, 1157, 1628
Mechanical properties	Value	Unit	Test Standard
Tensile modulus	1.67E6	psi	ISO 527-1, -2
Tensile stress at break, 5mm/min	25400	psi	ISO 527-1, -2
Tensile strain at break, 5mm/min	2.2	%	ISO 527-1, -2
Flexural modulus, 23°C	1.61E6	psi	ISO 178
Flexural strength, 23°C	32600	psi	ISO 178
Charpy impact strength, 23°C	13.3	ft-lb/in ²	ISO 179/1eU
Charpy impact strength, -30°C	13.3	ft-lb/in ²	ISO 179/1eU
Charpy notched impact strength, 23°C	4.19	ft-lb/in ²	ISO 179/1eA
Charpy notched impact strength, -30°C	4.19	ft-lb/in ²	ISO 179/1eA
Izod impact notched, 23°C	3.57	ft-lb/in ²	ISO 180/1A
Rockwell hardness (M-Scale)	123	M-Scale	ISO 2039-2
Ball indentation hardness, 30s	37700	psi	ISO 2039-1
Thermal properties	Value	Unit	Test Standard
Melting temperature, 10°C/min	486	°F	ISO 11357-1/-3
Glass transition temperature, 10°C/min	176	°F	ISO 11357-1,-2,-3
DTUL at 1.8 MPa	437	°F	ISO 75-1, -2
DTUL at 0.45 MPa	486	°F	ISO 75-1, -2
DTUL at 8.0 MPa	275	°F	ISO 75-1, -2
Vicat softening temperature, 50°C/h 50N	491	°F	ISO 306
Coeff. of linear therm expansion, parallel	0.117	E-4/°F	ISO 11359-2
Coeff. of linear therm expansion, normal	0.356	E-4/°F	ISO 11359-2
Limiting oxygen index (LOI)	25	%	ISO 4589-1/-2
Flammability @1.6mm nom. thickn.	HB	class	UL 94
thickness tested (1.6)	0.1	in	UL 94
Flammability at thickness h	HB	class	UL 94
thickness tested (h)	0.0315	in	UL 94
Electrical properties	Value	Unit	Test Standard
Dielectric constant (Dk), 100Hz	4.8	-	IEC 60250
Dielectric constant (Dk), 1MHz	4.2	-	IEC 60250
Dissipation factor, 100Hz	130	E-4	IEC 60250
Dissipation factor, 1MHz	180	E-4	IEC 60250
Volume resistivity, 23°C	2E14	Ohm*m	IEC 62631-3-1
Surface resistivity, 23°C	3E15	Ohm	IEC 62631-3-2
Electric strength, 23°C (AC)	838	kV/in	IEC 60243-1
Comparative tracking index	PLC 4	-	UL 746
Arc resistance	39	s	Internal

Diagrams

Stress-strain

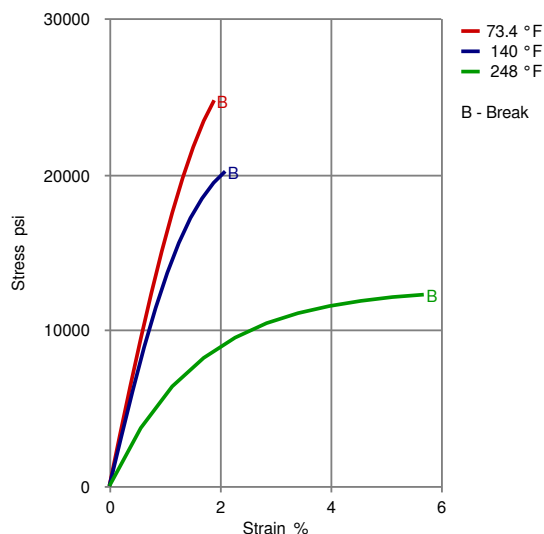

Secant modulus-strain

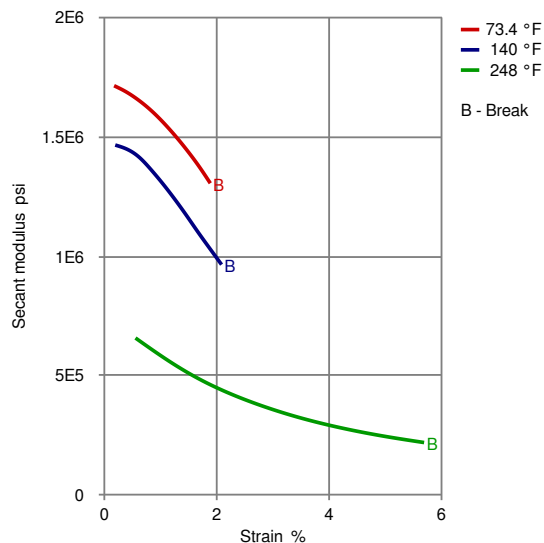

Typical injection moulding processing conditions

Pre Drying

	Value	Unit
Necessary low maximum residual moisture content	0.01	%
Drying time	2 - 4	h
Drying temperature	248 - 284	°F

Temperature

	Value	Unit
Hopper temperature	68 - 122	°F
Feeding zone temperature	104 - 140	°F
Zone1 temperature	500 - 518	°F
Zone2 temperature	518 - 536	°F
Zone3 temperature	536 - 554	°F
Zone4 temperature	536 - 554	°F
Nozzle temperature	518 - 554	°F
Melt temperature	518 - 554	°F
Mold temperature	275 - 293	°F
Hot runner temperature	518 - 554	°F

Speed

	Value
Injection speed	fast

Screw Speed

	Value	Unit
Screw speed diameter, 25mm	80	RPM
Screw speed diameter, 40mm	65	RPM
Screw speed diameter, 55mm	50	RPM

IMPET® 2700 GV1/30 - PET**Other text information****Pre-drying**

IMPET should in principle be predried. Because of the necessary low maximum residual moisture content the use of dry air dryers is recommended. The dew point should be $\leq -30^{\circ}\text{C}$. The time between drying and processing should be as short as possible.

Longer pre-drying times/storage

For subsequent storage of the material in the dryer until processed ($\leq 60\text{ h}$) it is necessary to lower the temperature to 100°C .

Injection molding

Melt Temperature $270\text{--}290^{\circ}\text{C}$
Mold Temperature $135\text{--}145^{\circ}\text{C}$
Maximum Barrel Residence Time *) $5\text{--}10\text{ min}$
Injection Speed fast
Peripheral screw speed max. $0,3\text{ m/sec}$
Back Pressure $10\text{--}20\text{ bar}$
Injection Pressure $600\text{--}900\text{ bar}$
Holding Pressure $300\text{--}500\text{ bar}$
Nozzle Design open design preferred

Injection speed, injection pressure and holding pressure have to be optimized to the individual article geometry. To avoid material degradation during processing low back pressure and minimum screw speed have to be used. Overheating of the material has to be avoided.

Ticona recommends only externally heated hot runner systems.

*) If the cylinder temperatures are higher than the recommended maximum temperatures, the max. residence time in the barrel has to be reduced.

Injection Molding Preprocessing

To avoid hydrolytic degradation during processing, IMPET resins have to be dried to a moisture level equal to or less than $0,01\%$. The drying should be done in a dry-air dryer (dew point $< -30^{\circ}\text{C}$) with a temperature of $120\text{ to }140^{\circ}\text{C}$ and a drying time of $2\text{ to }4\text{ hours}$. In case of longer residence times in the dry-air dryer, the temperature should be reduced to 100°C .

The time between drying and processing should be kept as short as possible. The processing machine feed hopper should be closed during the processing operation.

Characteristics

Special Characteristics	Auto spec approved, Heat resistant
Product Categories	Glass reinforced
Processing	Injection molding
Delivery Form	Pellets
Additives	Release agent

Other Approvals

OEM	Specification	Additional Information
Mercedes-Benz Group (Daimler)		Lighting
Geely	Q/JL J124006	2010