

**IMPET® 2700 GV1/45 - PET****Description**

45% glass fiber reinforced

Polyethylene terephthalate, 45 % glass filled, high flowability, excellent gloss, high modulus, very high heat deflection temperature.

Physical properties

	Value	Unit	Test Standard
Density	109	lb/ft ³	ISO 1183
Molding shrinkage, parallel (flow)	0.2 - 0.3	%	ISO 294-4, 2577
Molding shrinkage, transverse normal	0.6 - 0.8	%	ISO 294-4, 2577
Water absorption, 23°C-sat	0.4	%	Sim. to ISO 62
Humidity absorption, 23°C/50%RH	0.15	%	ISO 62
Viscosity number	1940	in ³ /lb	ISO 307, 1157, 1628

Mechanical properties





	Value	Unit	Test Standard
Tensile modulus	2.47E6	psi	ISO 527-1, -2
Tensile stress at break, 5mm/min	29000	psi	ISO 527-1, -2
Tensile strain at break, 5mm/min	1.75	%	ISO 527-1, -2
Flexural modulus, 23°C	2.47E6	psi	ISO 178
Flexural strength, 23°C	34800	psi	ISO 178
Charpy impact strength, 23°C	16.6	ft-lb/in ²	ISO 179/1eU
Charpy impact strength, -30°C	14.7	ft-lb/in ²	ISO 179/1eU
Charpy notched impact strength, 23°C	5.71	ft-lb/in ²	ISO 179/1eA
Charpy notched impact strength, -30°C	6.18	ft-lb/in ²	ISO 179/1eA
Izod impact notched, 23°C	6.18	ft-lb/in ²	ISO 180/1A
Rockwell hardness (M-Scale)	121	M-Scale	ISO 2039-2
Ball indentation hardness, 30s	43500	psi	ISO 2039-1





Thermal properties



	Value	Unit	Test Standard
Melting temperature, 10°C/min	482	°F	ISO 11357-1/-3
DTUL at 1.8 MPa	442	°F	ISO 75-1, -2
DTUL at 0.45 MPa	486	°F	ISO 75-1, -2
DTUL at 8.0 MPa	338	°F	ISO 75-1, -2
Vicat softening temperature, 50°C/h 50N	491	°F	ISO 306
Coeff. of linear therm expansion, parallel	0.0833	E-4/°F	ISO 11359-2
Coeff. of linear therm expansion, normal	0.556	E-4/°F	ISO 11359-2
Limiting oxygen index (LOI)	26	%	ISO 4589-1/-2
Flammability @1.6mm nom. thickn. thickness tested (1.6)	HB	class	UL 94
Flammability at thickness h thickness tested (h)	0.1	in	UL 94
	HB	class	UL 94
	0.0315	in	UL 94

Electrical properties

	Value	Unit	Test Standard
Dielectric constant (Dk), 100Hz	5.2	-	IEC 60250
Dielectric constant (Dk), 1MHz	4.5	-	IEC 60250
Dissipation factor, 100Hz	30	E-4	IEC 60250
Dissipation factor, 1MHz	165	E-4	IEC 60250
Volume resistivity, 23°C	1E14	Ohm*m	IEC 62631-3-1
Surface resistivity, 23°C	>1E14	Ohm	IEC 62631-3-2
Electric strength, 23°C (AC)	889	kV/in	IEC 60243-1
Comparative tracking index	PLC 3	-	UL 746
Arc resistance	110	s	Internal

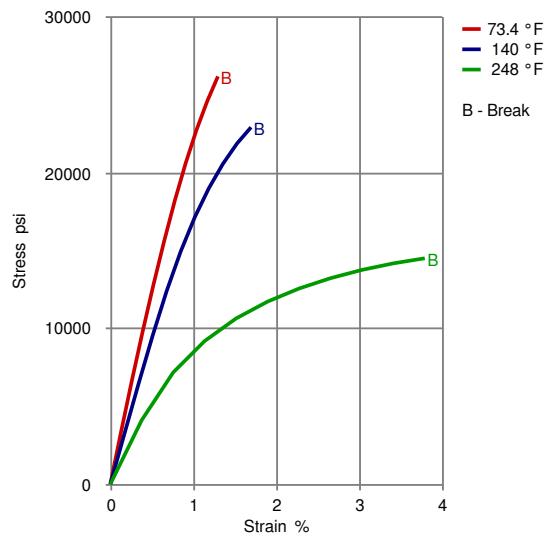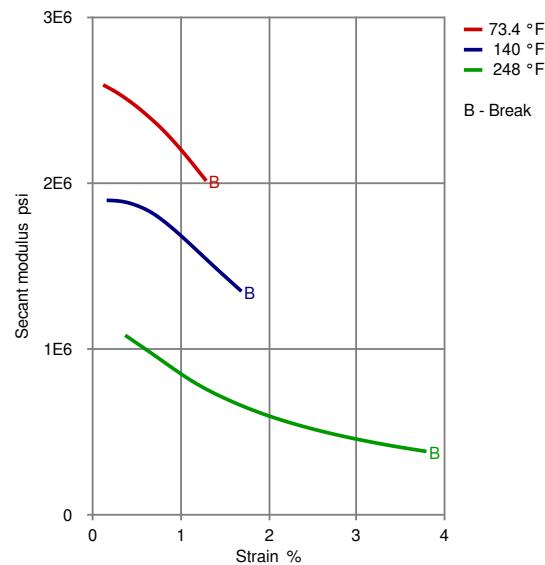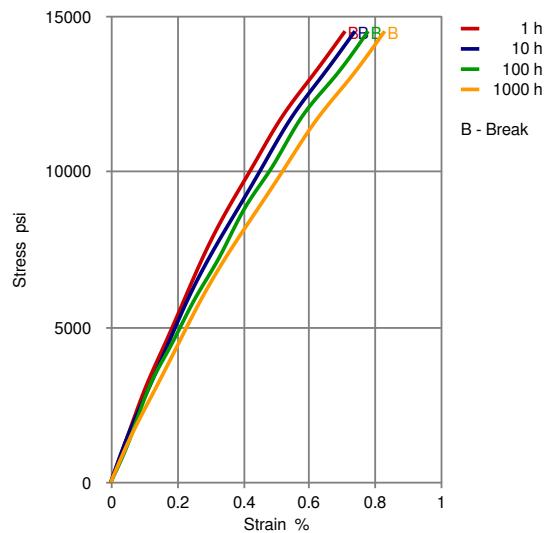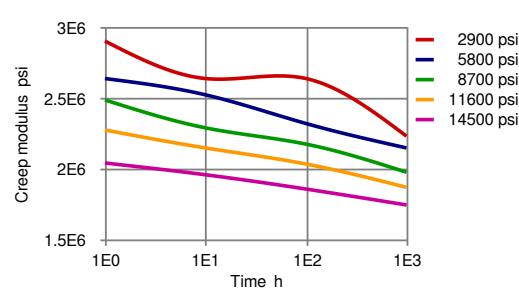Diagrams**Stress-strain****Secant modulus-strain****CAMPUS Stress-strain (isochronous) 73.4 °F****CAMPUS Creep modulus-time 73.4 °F**

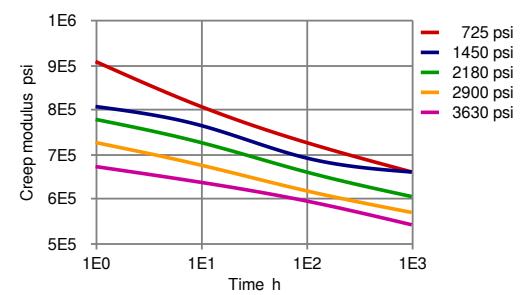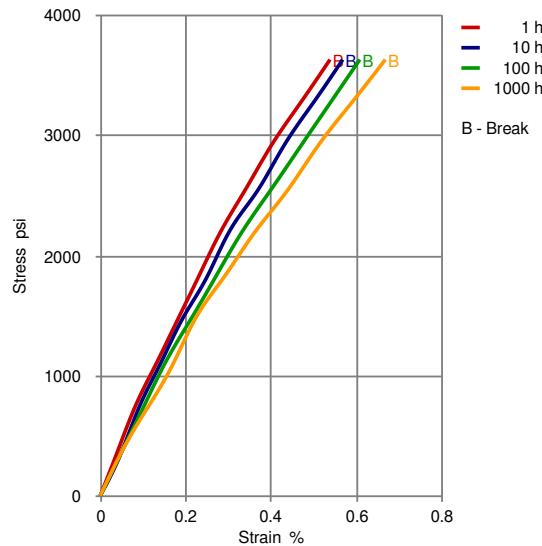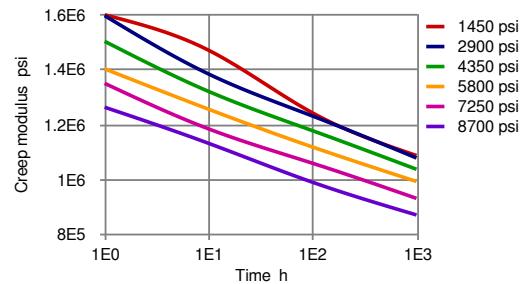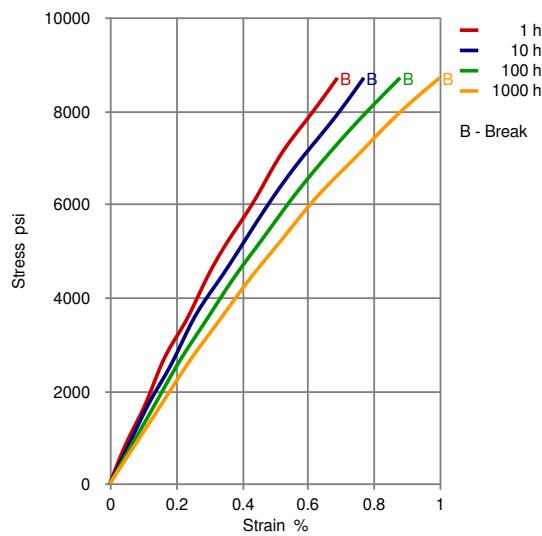

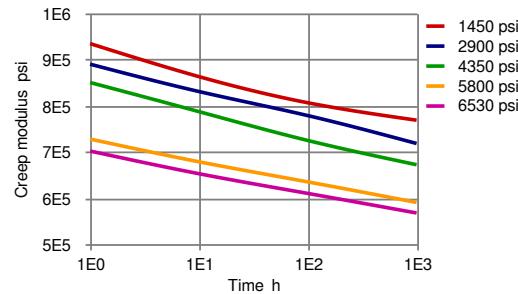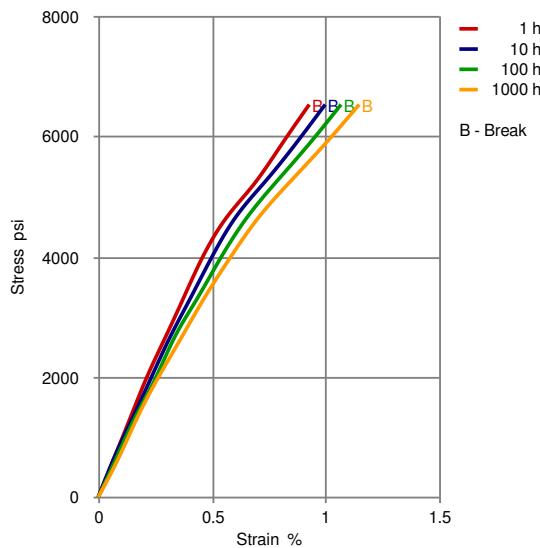

Typical injection moulding processing conditions

Pre Drying

	Value	Unit
Necessary low maximum residual moisture content	0.01	%
Drying time	2 - 4	h
Drying temperature	248 - 284	°F

Temperature

	Value	Unit
Hopper temperature	68 - 122	°F
Feeding zone temperature	104 - 140	°F
Zone1 temperature	500 - 518	°F
Zone2 temperature	518 - 536	°F
Zone3 temperature	536 - 554	°F
Zone4 temperature	536 - 554	°F
Nozzle temperature	518 - 554	°F
Melt temperature	518 - 554	°F
Mold temperature	275 - 293	°F
Hot runner temperature	518 - 554	°F

Speed

	Value
Injection speed	fast

Screw Speed

	Value	Unit
Screw speed diameter, 25mm	80	RPM
Screw speed diameter, 40mm	65	RPM
Screw speed diameter, 55mm	50	RPM

Other text information

Pre-drying

IMPET should in principle be predried. Because of the necessary low maximum residual moisture content the use of dry air dryers is recommended. The dew point should be =< - 30 ° C. The time between drying and processing should be as short as possible.

Longer pre-drying times/storage

For subsequent storage of the material in the dryer until processed (<= 60 h) it is necessary to lower the temperature to 100 ° C.

IMPET® 2700 GV1/45 - PET**Injection molding**

Melt Temperature 270-290 °C
 Mold Temperature 135-145 °C
 Maximum Barrel Residence Time *) 5-10 min
 Injection Speed fast
 Peripheral screw speed max.0,3 m/sec
 Back Pressure 10-20 bar
 Injection Pressure 600-900 bar
 Holding Pressure 300-500 bar
 Nozzle Design open design preferred

Injection speed, injection pressure and holding pressure have to be optimized to the individual article geometry. To avoid material degradation during processing low back pressure and minimum screw speed have to be used. Overheating of the material has to be avoided.

Ticona recommends only externally heated hot runner systems.

*) If the cylinder temperatures are higher than the recommended maximum temperatures, the max. residence time in the barrel has to be reduced.

Injection Molding Preprocessing

To avoid hydrolytic degradation during processing, IMPET resins have to be dried to a moisture level equal to or less than 0,01%. The drying should be done in a dry-air dryer (dew point < -30°C) with a temperature of 120 to 140 °C and a drying time of 2 to 4 hours. In case of longer residence times in the dry-air dryer, the temperature should be reduced to 100°C.
 The time between drying and processing should be kept as short as possible. The processing machine feed hopper should be closed during the processing operation.

Characteristics

Special Characteristics	Auto spec approved, Heat resistant
Product Categories	Glass reinforced
Processing	Injection molding
Delivery Form	Pellets
Additives	Release agent

Other Approvals

OEM	Specification	Additional Information
Continental		No spec listed