

CELSTRAN® PP-GF50-04 Natural | PP | Glass Reinforced

Description

Material code according to ISO 1043-1: PP

Heat stabilized polypropylene reinforced with 50 weight percent long glass fibers. The fibers are chemically coupled to the polypropylene matrix. The pellets are cylindrical and normally as well as the embedded fibers 10 mm long. (-0403 = heat stabilized, -0453 = low emission)

Parts molded of CELSTRAN have outstanding mechanical properties such as high strength and stiffness combined with high heat deflection. The notched impact strength is increased at elevated and low temperatures due to the fiber skeleton built in the parts. The long fiber reinforcement reduces creep significantly.

The very isotropic shrinkage in the molded parts minimizes the warpage.

Complex parts can be manufactured with high reproducibility by injection molding.

Application field: Functional/structural parts for automotive


Physical properties	Value	Unit	Test Standard
Density	1340	kg/m ³	ISO 1183

Mechanical properties	Value	Unit	Test Standard
Tensile modulus (1mm/min)	12000	MPa	ISO 527-2/1A
Tensile modulus (80°C)	8500	MPa	ISO 527-2/1A
Tensile strength (80°C)	90	MPa	ISO 527-2/1A
Tensile stress at break (5mm/min)	145	MPa	ISO 527-2/1A
Tensile strain at break (5mm/min)	2	%	ISO 527-2/1A
Elongation at break (80°C)	2.2	%	ISO 527-2/1A
Flexural modulus (23°C)	12900	MPa	ISO 178
Flexural modulus (80°C)	9000	MPa	ISO 178
Flexural strength (23°C)	235	MPa	ISO 178
Flexural strength (80°C)	130	MPa	ISO 178
Charpy impact strength @ 23°C	80.0	kJ/m ²	ISO 179/1eU
Charpy impact strength @ -30°C	75.0	kJ/m ²	ISO 179/1eU
Charpy notched impact strength @ 23°C	35.0	kJ/m ²	ISO 179/1eA
Charpy notched impact strength @ -30°C	38.0	kJ/m ²	ISO 179/1eA


Thermal properties	Value	Unit	Test Standard
Melting temperature (10°C/min)	165	°C	ISO 11357-1,-2,-3
DTUL @ 1.8 MPa	159	°C	ISO 75-1/-2

CELSTRAN® PP-GF50-04 Natural | PP | Glass Reinforced


Stress-strain

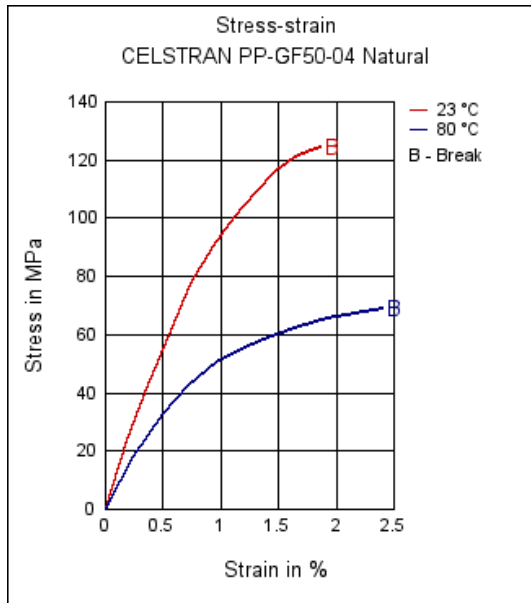

Secant modulus-strain

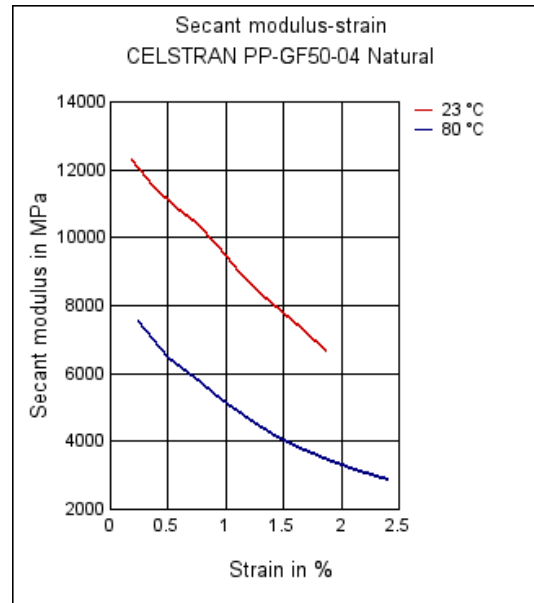

Typical injection moulding processing conditions

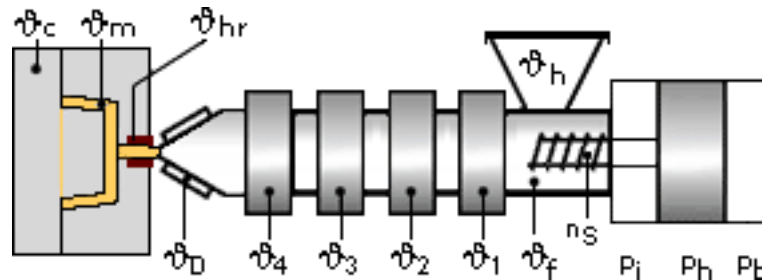

Pre Drying:

Necessary low maximum residual moisture content: 0.2%

It is normally not necessary to dry CELSTRAN PP

Drying time: 2 h

Drying temperature: 90 - 100 °C

Temperature:

	$\varnothing_{\text{Manifold}}$	$\varnothing_{\text{Mold}}$	$\varnothing_{\text{Melt}}$	$\varnothing_{\text{Nozzle}}$	$\varnothing_{\text{Zone4}}$	$\varnothing_{\text{Zone3}}$	$\varnothing_{\text{Zone2}}$	$\varnothing_{\text{Zone1}}$	$\varnothing_{\text{Feed}}$
min (°C)	260	40	260	280	280	270	260	250	20
max (°C)	290	70	290	290	290	280	270	260	50

CELSTRAN® PP-GF50-04 Natural | PP | Glass Reinforced

Pressure:

	Inj press	Hold press	Back pressure
min (bar)	600	400	0
max (bar)	1200	800	30

Speed:

Injection speed: slow

Screw speed

Screw diameter (mm)	16	25	40	55	75
Screw speed (RPM)	-	-	50	35	25

Special Info:

Assessment of mechanical values using an injection molding machine with dedicated screw. Implementation: Feb. 2010